

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址: 中国广州市天河区珠江新城花城大道66号B座
网址: www.iqtc.cn 邮编: 510623
Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China
Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 1 of 14

UN38.3 报告

UN38.3 Test Report

样品名称: 锂离子电池

Sample Name: Li-ion Battery

委托单位: 湖北亿纬动力有限公司

Applicant: EVE POWER Co., Ltd.



Q6YXQI6N7X

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.
2. 未经签发机构书面同意, 不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 2 of 14

检测证书 TEST REPORT

样品名称 Sample Name	锂离子电池 Li-ion Battery		
型号 Model	LF230		
委托单位 Applicant	湖北亿纬动力有限公司 EVE POWER Co., Ltd.		
委托单位地址 Applicant Address	荆门高新区·掇刀区荆南大道 68 号 NO.68, Jingnan Avenue, Hi-tech Zone, Duodao District, Jingmen, Hubei		
生产单位 Manufacture	湖北亿纬动力有限公司 EVE POWER Co., Ltd.		
生产单位地址 Manufacture Address	荆门高新区·掇刀区荆南大道 68 号 NO.68, Jingnan Avenue, Hi-tech Zone, Duodao District, Jingmen, Hubei		
样品外观与性状 Appearance & Odor	蓝色塑料外壳 Blue plastic shell		
测试方法和判定标准 Test method and criterion	联合国《关于危险货物运输的建议书 试验和标准手册》ST/SG/AC.10/11/Rev.7, 38.3 UNITED NATIONS "Recommendations on the TRANSPORT OF DANGEROUS GOODS", Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3		
接样时间 Accepted date	2020-05-28	测试日期 Test date	2020-05-28~2020-08-05
测试项目 Test items	高度模拟、温度试验、振动、冲击、外部短路、挤压、强制放电。 Altitude simulation, Thermal test, Vibration, Shock, External short circuit, Crush, Forced discharge.		
结论 Conclusion	经测试，该样品符合联合国《关于危险货物运输的建议书 试验和标准手册》 ST/SG/AC.10/11/Rev.7, 38.3 标准要求。 The sample has passed the test items of UNITED NATIONS "Recommendations on the TRANSPORT OF DANGEROUS GOODS" Manual of Test and Criteria ST/SG/AC.10/11/Rev.7, 38.3.		
备注 Remark	1.检测结果仅对样品有效； The test results are only valid for the test samples submitted to the applicant. 2.随附 UN38.3 试验概要（编号：01052000003024-2(E)）。 Attached with UN38.3 test summary (No.: 01052000003024-2(E)).		

批准

Approver:

陆玲强

审核

Checker:

莫子君

主检

Appraiser:

解昌龙

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 3 of 14

电池信息：

The battery information:

电池类型 Battery type	锂离子电池 Lithium ion batteries	标称电压 Nominal Voltage	3.2V
额定容量 Rated Capacity	230Ah	总能量 Total Energy	736Wh
充电限制电压 Limited Charge Voltage	3.65V	标准充电电流 Standard Charge Current	115A
最大充电电流 Maximum Charge Current	230A	充电截止电流 Charge Cut-off Current	11.5A
标准放电电流 Standard discharge Current	115A	最大放电电流 Maximum Discharge Current	230A
放电截止电压 Discharge Cut-off Voltage	2.5V	物理形状说明 Physical description	长方体 Cuboid 207.0 ± 1.0mm(W) × 173.9 ± 1.0mm(D) × 54.0 ± 1.0mm(H)
电芯数量 Cell Quantity	1 PCS	重量 Mass	4110 ± 100g
电芯容量 Cell Capacity	230Ah	电芯型号 Cell Model	LF230
电芯生产单位 Manufacturer of cell	湖北亿纬动力有限公司 EVE POWER Co., Ltd		

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 4 of 14

序号 No.	测试项目名称 Name of test	标准要求或标准条款号 Stand requirement or the clause number of standard	测试结果 Test result	本项结论 Test conclusion	备注 Remark	
1	高度模拟 Altitude simulation	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.1 Test T.1	见附表 1 See Appendix 1	合格 Passed	/	
2	温度循环 Thermal test	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.2 Test T.2	见附表 2 See Appendix 2	合格 Passed	/	
3	振动 Vibration	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.3 Test T.3	见附表 3 See Appendix 3	合格 Passed	/	
4	冲击 Shock	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.4 Test T.4	见附表 4 See Appendix 4	合格 Passed	/	
5	外部短路 External short circuit	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.5 Test T.5	见附表 5 See Appendix 5	合格 Passed	/	
6	挤压 Crush	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.6 Test T.6	见附表 6 See Appendix 6	合格 Passed	/	
7	过度充电 Overcharge	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.7 Test T.7	见附表 7 See Appendix 7	不适用 Not applicable	/	
8	强制放电 Forced discharge	联合国《关于危险货物运输的建议书 试验和标准手册》UN Manual of Tests and Criteria ST/SG/AC.10/11/Rev.7, 38.3 试验 T.8 Test T.8	见附表 8 See Appendix 8	合格 Passed	/	
测试环境 Test environment condition		环境温度：20℃-25℃；环境湿度：45%-75% Ambient temperature: 20℃-25℃, Ambient humidity: 45%-75%				
分包测试情况 Subcontracted test condition		测试项目 Test items	/			
		分包实验室 Subcontracted Laboratory	名称 Name	/	邮编 Post code	/
			地址 Address	/	电话 Tel	/

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 5 of 14

序号 No.	附表 1 Appendix 1	测试项目名称 Name of test	高度模拟 Altitude simulation				
标准要求 Requirement of Standard	<p>试验电池或电池组在压力等于或低于 11.6kPa 和环境温度 20℃±5℃ 下存放至少 6h。试验电池或电池组应无重量损失、无渗漏、无排气、无解体、无破裂和无燃烧，并且每个试验电池或电池组在试验后的开路电压不少于其在进行这一试验前电压的 90%（完全放电状态的试验电池或电池组除外）。</p> <p>Test cells and batteries shall be stored at a pressure of 11.6 kPa or less for at least six hours at ambient temperature 20 ± 5 °C. Cells and batteries meet this requirement if there is no mass loss, no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.</p>						
样品状态 Sample status	<p>C1#~C5#: 第一个循环完全充电的电池； C1#~C5#: first cycle in fully charged states. C6#~C10#: 第二十五个循环完全充电的电池。 C6#~C10#: after 25 cycles ending in fully charged states.</p>						
样品编号 Sample No.	测试前 Before		测试后 After		质量损失 Mass loss (%)	剩余电压 Residual OCV(%)	测试结果 Test result
	电池质量 m ₁ (g)	开路电压 v ₁ (v)	电池质量 m ₂ (g)	开路电压 v ₂ (v)			
C1#	4147.0	3.39	4147.0	3.39	0.000	100.00	O
C2#	4170.8	3.40	4170.7	3.39	0.002	99.71	O
C3#	4156.2	3.40	4156.2	3.39	0.000	99.71	O
C4#	4148.9	3.39	4148.7	3.39	0.005	100.00	O
C5#	4166.4	3.40	4166.4	3.39	0.000	99.71	O
C6#	4160.1	3.40	4160.1	3.39	0.000	99.71	O
C7#	4146.5	3.40	4146.5	3.39	0.000	99.71	O
C8#	4161.7	3.40	4161.6	3.39	0.002	99.71	O
C9#	4148.5	3.40	4148.5	3.39	0.000	99.71	O
C10#	4149.2	3.39	4149.2	3.39	0.000	100.00	O
<p>注：L-泄漏； V-排气； D-解体； R-破裂； F-起火； O-无泄漏、无排气、无解体、无破裂、无起火。 Note: L-Leakage, V-Venting, D-Disassembly, R-Rupture, F-Fire, O- No Leakage, No Venting, No Disassembly, No Rupture & No Fire.</p>							

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 0105200003024-1(E)

Date: 2020-08-05

Page: 6 of 14

序号 No.	附表 2 Appendix 2	测试项目名称 Name of test	温度循环 Thermal test				
标准要求 Requirement of Standard	<p>试验电池或电池组在试验温度等于 $72^{\circ}\text{C}\pm 2^{\circ}\text{C}$ 下存放至少 6h，接着在试验温度等于 $-40^{\circ}\text{C}\pm 2^{\circ}\text{C}$ 下存放至少 6h（大型电池或电池组暴露于极端试验温度的时间至少为 12h）。两个极端试验温度之间的最大时间间隔为 30min。重复 10 次，再将所有试验电池或电池组在环境温度 $20^{\circ}\text{C}\pm 5^{\circ}\text{C}$ 下存放 24h。试验电池或电池组应无重量损失、无渗漏、无排气、无解体、无破裂和无燃烧，并且每个试验电池或电池组在试验后的开路电压不少于其在进行这一试验前电压的 90%（完全放电状态的试验电池或电池组除外）。</p> <p>Test cells and batteries are to be stored for at least six hours at a test temperature equal to $72 \pm 2^{\circ}\text{C}$, followed by storage for at least six hours at a test temperature equal to $-40 \pm 2^{\circ}\text{C}$. The maximum time interval between test temperature extremes is 30 minutes. This procedure is to be repeated 10 times, after which all test cells and batteries are to be stored for 24 hours at ambient temperature ($20 \pm 5^{\circ}\text{C}$). For large cells and batteries the duration of exposure to the test temperature extremes should be at least 12 hours. Cells and batteries meet this requirement if there is no mass loss, no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.</p>						
样品状态 Sample status	<p>C1#~C5#: 第一个循环完全充电的电池； C1#~C5#: first cycle in fully charged states. C6#~C10#: 第二十五个循环完全充电的电池。 C6#~C10#: after 25 cycles ending in fully charged states.</p>						
样品编号 Sample No.	测试前 Before		测试后 After		质量损失 Mass loss (%)	剩余电压 Residual OCV(%)	测试结果 Test result
	电池质量 $m_1(\text{g})$	开路电压 $v_1(\text{v})$	电池质量 $m_2(\text{g})$	开路电压 $v_2(\text{v})$			
C1#	4147.0	3.39	4146.5	3.37	0.012	99.41	O
C2#	4170.7	3.39	4170.4	3.36	0.007	99.12	O
C3#	4156.2	3.39	4155.8	3.37	0.010	99.41	O
C4#	4148.7	3.39	4148.2	3.37	0.012	99.41	O
C5#	4166.4	3.39	4166.0	3.37	0.010	99.41	O
C6#	4160.1	3.39	4159.8	3.36	0.007	99.12	O
C7#	4146.5	3.39	4146.2	3.36	0.007	99.12	O
C8#	4161.6	3.39	4161.3	3.36	0.007	99.12	O
C9#	4148.5	3.39	4148.1	3.37	0.010	99.41	O
C10#	4149.2	3.39	4148.8	3.37	0.010	99.41	O
<p>注：L-泄漏； V-排气； D-解体； R-破裂； F-起火； O-无泄漏、无排气、无解体、无破裂、无起火。 Note:L-Leakage, V-Venting, D-Disassembly, R-Rupture, F-Fire, O- No Leakage, No Venting, No Disassembly, No Rupture & No Fire.</p>							

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 7 of 14

序号 No.	附表 3 Appendix 3	测试项目名称 Name of test	振动 Vibration				
标准要求 Requirement of Standard	<p>将电池或电池组直接安装或通过夹具安装在振动台的台面上，用正弦波，频率在 7Hz 和 200Hz 之间摆动再回到 7Hz 的对数扫频 15min，对三个互相垂直的电池或电池组安装方向的每个方向重复进行 12 次，一共振动 3h。试验电池或电池组应无重量损失、无渗漏、无排气、无解体、无破裂和无燃烧，并且每个试验电池或电池组在试验后的开路电压不少于其在进行这一试验前电压的 90%（完全放电状态的试验电池或电池组除外）。</p> <p>Cells and batteries are firmly secured to the platform of the vibration machine without distorting the cells in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 Hz and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of three mutually perpendicular mounting positions of the cell. One of the directions of vibration must be perpendicular to the terminal face. Cells and batteries meet this requirement if there is no mass loss, no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.</p>						
样品状态 Sample status	<p>C1#~C5#: 第一个循环完全充电的电池； C1#~C5#: first cycle in fully charged states. C6#~C10#: 第二十五个循环完全充电的电池。 C6#~C10#: after 25 cycles ending in fully charged states.</p>						
样品编号 Sample No.	测试前 Before		测试后 After		质量损失 Mass loss (%)	剩余电压 Residual OCV(%)	测试结果 Test result
	电池质量 $m_1(g)$	开路电压 $v_1(v)$	电池质量 $m_2(g)$	开路电压 $v_2(v)$			
C1#	4146.5	3.37	4146.5	3.36	0.000	99.70	O
C2#	4170.4	3.36	4170.2	3.36	0.005	100.00	O
C3#	4155.8	3.37	4155.8	3.37	0.000	100.00	O
C4#	4148.2	3.37	4148.2	3.37	0.000	100.00	O
C5#	4166.0	3.37	4165.8	3.36	0.005	99.70	O
C6#	4159.8	3.36	4159.8	3.36	0.000	100.00	O
C7#	4146.2	3.36	4146.2	3.36	0.000	100.00	O
C8#	4161.3	3.36	4161.2	3.36	0.002	100.00	O
C9#	4148.1	3.37	4148.1	3.36	0.000	99.70	O
C10#	4148.8	3.37	4148.8	3.37	0.000	100.00	O
<p>注：L-泄漏； V-排气； D-解体； R-破裂； F-起火； O-无泄漏、无排气、无解体、无破裂、无起火。 Note:L-Leakage, V-Venting, D-Disassembly, R-Rupture, F-Fire, O- No Leakage, No Venting, No Disassembly, No Rupture & No Fire.</p>							

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 0105200003024-1(E)

Date: 2020-08-05

Page: 8 of 14

序号 No.	附表 4 Appendix 4	测试项目名称 Name of test	冲击 Shock				
标准要求 Requirement of Standard	<p>将电池或电池组用坚硬支架紧固在试验装置上，对于小型电池组，应以加速度为 150gn 或 $gn = \sqrt{100850 / mass}$ 中较小者的正弦波冲击，脉冲持续时间 6ms，按三个相互垂直的轴向分别对其正负极各冲击 3 次，共冲击 18 次。各试验电池或电池组应无重量损失、无渗漏、无排气、无解体、无破裂和无燃烧，并且每个试验电池或电池组在试验后的开路电压不少于其在进行这一试验前电压的 90%（完全放电状态的试验电池或电池组除外）。</p> <p>Test cells and batteries shall be secured to the testing machine by means of a rigid mount which will support all mounting surfaces of each test battery. Each small batteries shall be subjected to a half-sine shock of peak acceleration of 150gn or acceleration (gn) = $\sqrt{100850 / mass}$ and pulse duration of 6 milliseconds. Each cell or battery shall be subjected to three shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicular mounting positions of the cell or battery for a total of 18 shocks. Cells and batteries meet this requirement if there is no mass loss, no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.(NOTE: Mass is expressed in kilograms)</p>						
样品状态 Sample status	<p>C1#~C5#: 第一个循环完全充电的电池； C1#~C5#: first cycle in fully charged states. C6#~C10#: 第二十五个循环完全充电的电池。 C6#~C10#: after 25 cycles ending in fully charged states.</p>						
样品编号 Sample No.	测试前 Before		测试后 After		质量损失 Mass loss (%)	剩余电压 Residual OCV(%)	测试结果 Test result
	电池质量 $m_1(g)$	开路电压 $v_1(v)$	电池质量 $m_2(g)$	开路电压 $v_2(v)$			
C1#	4146.5	3.36	4146.5	3.36	0.000	100.00	O
C2#	4170.2	3.36	4170.2	3.36	0.000	100.00	O
C3#	4155.8	3.37	4155.8	3.37	0.000	100.00	O
C4#	4148.2	3.37	4148.2	3.36	0.000	99.70	O
C5#	4165.8	3.36	4165.8	3.36	0.000	100.00	O
C6#	4159.8	3.36	4159.8	3.36	0.000	100.00	O
C7#	4146.2	3.36	4146.2	3.36	0.000	100.00	O
C8#	4161.2	3.36	4161.2	3.36	0.000	100.00	O
C9#	4148.1	3.36	4148.1	3.36	0.000	100.00	O
C10#	4148.8	3.37	4148.8	3.36	0.000	99.70	O
<p>注：L-泄漏； V-排气； D-解体； R-破裂； F-起火； O-无泄漏、无排气、无解体、无破裂、无起火。 Note:L-Leakage, V-Venting, D-Disassembly, R-Rupture, F-Fire, O- No Leakage, No Venting, No Disassembly, No Rupture & No Fire.</p>							

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址: 中国广州市天河区珠江新城花城大道66号B座

网址: www.iqtc.cn 邮编: 510623

Address: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 9 of 14

序号 No.	附表 5 Appendix 5	测试项目名称 Name of test	外部短路 External short circuit	
标准要求 Requirement of Standard	待试验电池或电池组的外壳温度稳定在 $57\pm 4^{\circ}\text{C}$ 后, 在 $57\pm 4^{\circ}\text{C}$ 下使电池或电池组经受总外电阻小于 0.1Ω 的短路条件, 当电池或电池组外壳温度回到 $57\pm 4^{\circ}\text{C}$ 后继续至少 1h, 然后短路断开, 再观察电池或电池组 6h 才结束试验。电池或电池组的外壳温度应不超过 170°C , 并且试验后 6h 内应无解体、无破裂和无燃烧。 The cell or battery to be tested shall be temperature stabilized so that its external case temperature reaches $57\pm 4^{\circ}\text{C}$ and then the cell or battery shall be subjected to a short circuit condition with a total external resistance of less than 0.1 ohm at $57\pm 4^{\circ}\text{C}$. This short circuit condition is continued for at least one hour after the cell or battery external case temperature has returned to $57\pm 4^{\circ}\text{C}$. The cell or battery must be observed for a further six hours for the test to be concluded. Cells and batteries meet this requirement if their external temperature does not exceed 170°C and there is no disassembly, no rupture and no fire within six hours of this test			
样品状态 Sample status	C1#~C5#: 第一个循环完全充电的电池; C1#~C5#: first cycle in fully charged states. C6#~C10#: 第二十五个循环完全充电的电池。 C6#~C10#: after 25 cycles ending in fully charged states.			
样品编号 Sample No.	样品表面最高温度 Max External Temperature($^{\circ}\text{C}$)	测试结果 Test result	备注 Remark	
C1#	82.6	O	/	
C2#	84.0	O	/	
C3#	79.7	O	/	
C4#	88.6	O	/	
C5#	82.4	O	/	
C6#	78.8	O	/	
C7#	80.9	O	/	
C8#	81.2	O	/	
C9#	86.5	O	/	
C10#	88.0	O	/	
注: D-解体; R-破裂; F-起火; O-无解体、无破裂、无起火。 Note: D-Disassembly, R-Rupture, F-Fire, O-No Disassembly, No Rupture & No Fire.				

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意, 不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 10 of 14

序号 No.	附表 6 Appendix 6	测试项目名称 Name of test		挤压 Crush			
标准要求 Requirement of Standard	<p>适用于棱柱形、袋装、硬币/纽扣电池和直径小于 18mm 的圆柱形电池)： 将电池或元件电池放在两个平面之间挤压，挤压力度逐渐加大，在第一个接触点上的速度大约为 1.5cm/s。挤压持续进行，直到出现以下三种情况之一即解除压力： (a)施加的力量达到 13kN±0.78kN； (b)电池的电压下降至少 100mV；或 (c)电池变形达原始厚度的 50%或以上。 棱柱形或袋装电池应从最宽的一面施压。纽扣/硬币电池应从其平坦表面施压。圆柱形电池应从与纵轴垂直的方向施压。每个电池只做一次挤压试验。 试验电池或电池组的组成电芯外部温度不超过 170℃，并且在试验过程中和试验后 6 小时内应无解体、无破裂、无起火。 Crush(applicable to prismatic, pouch, coin/button cells and cylindrical cells less than 18 in diameter):A cell or component cell is to be crushed between two flat surfaces. The crushing is to be gradual with a speed of approximately 1.5cm/s at the first point of contact. The crushing is to be continued until the first of the three options below is reached. (a)The applied force reaches 13kN±0.78kN; (b)The voltage of the cell drops by at least 100mV;or (c)The cell is deformed by 50% or more of its original thickness. Once the maximum pressure has been obtained, the voltage drops by 100mV or more, or the cell is deformed by at least 50% of its original thickness, the pressure shall be released. Each test cell or component cell is to be subjected to one crush only. Cells and component cells meet this requirement if their external temperature does not exceed 170 °C and there is no disassembly and no fire during the test and within six hours after this test.</p>						
样品状态 Sample status	<p>C11#~C15#: 第一个循环 50%的额定容量的电芯。 C11#~C15#: first cycle at 50% of the design rated capacity of cell. C16#~C20#: 第二十五个循环 50%的额定容量的电芯。 C16#~C20#: after 25 cycles at 50% of the design rated capacity of cell.</p>						
样品编号 Sample No.	样品表面最高温度 Max External Temperature(°C)	测试结果 Test result	备注 Remark	样品编号 Sample No.	样品表面最高温度 Max External Temperature(°C)	测试结果 Test result	备注 Remark
C11#	26.8	O	/	C16#	27.1	O	/
C12#	26.2	O	/	C17#	27.1	O	/
C13#	25.9	O	/	C18#	26.5	O	/
C14#	26.3	O	/	C19#	26.8	O	/
C15#	25.6	O	/	C20#	26.3	O	/
<p>注： D-解体； R-破裂； F-起火； O-无解体、无破裂、无起火。 Note: D-Disassembly, R-Rupture, F-Fire, O-No Disassembly, No Rupture & No Fire.</p>							

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 11 of 14

序号 No.	附表 7 Appendix 7	测试项目名称 Name of test	过度充电 Overcharge
标准要求 Requirement of Standard	<p>充电电流必须是制造商建议的最大连续充电电流的两倍，试验的最小电压应为如下：</p> <p>(a) 制造商建议的充电电压不大于 18V 时，试验的最小电压应是电池组最大充电电压的两倍或 22V 两者中的较少者。</p> <p>(b) 制造商建议的充电电压大于 18V 时，试验的最小电压应是最大充电电压的 1.2 倍。</p> <p>可再充电电池组在环境温度下试验 24h。试样在试验后 7 天内应无解体和无燃烧。</p> <p>The charge current shall be twice the manufacturer's recommended maximum continuous charge current. The minimum voltage of the test shall be as follows:</p> <p>(a) When the manufacturer's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V.</p> <p>(b) When the manufacturer's recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage.</p> <p>Tests are to be conducted at ambient temperature. The duration of the test shall be 24 hours. Rechargeable batteries meet this requirement if there is no disassembly and no fire within seven days of the test.</p>		
样品状态 Sample status	/		
样品编号 Sample No.	测试结果 Test result		备注 Remark
/	/		<p>未安装过度充电保护装置、按设计要求只能用在另一个带过度充电保护装置的电池组或设备中的电池组或单一电池组，无需满足本项试验的要求。</p> <p>Batteries or single cell batteries not equipped with battery overcharge protection that are designed for use only as a component in another battery or in equipment, which affords such protection, are not subject to the requirements of this test.</p>
/	/		
/	/		
/	/		
<p>注：D-解体；R-破裂；F-起火；O-无解体、无破裂、无起火。</p> <p>Note: D-Disassembly, R-Rupture, F-Fire, O-No Disassembly, No Rupture & No Fire.</p>			

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 12 of 14

序号 No.	附表 8 Appendix 8	测试项目名称 Name of test	强制放电 Forced discharge		
标准要求 Requirement of Standard	<p>试验原电池或可再充电电池在环境温度下与 12V 的直流电源串联，在起始电流等于制造商给定的最大放电电流的条件下强制放电。原电池或可再充电电池在试验后 7 天内应无解体和无燃烧。</p> <p>Each cell shall be forced discharged at ambient temperature by connecting it in series with a 12 V D.C. power supply at an initial current equal to the maximum discharge current specified by the manufacturer. The specified discharge current is to be obtained by connecting a resistive load of the appropriate size and rating in series with the test cell. Each cell shall be forced discharged for a time interval (in hours) equal to its rated capacity divided by the initial test current (in Ampere). Primary or rechargeable cells meet this requirement if there is no disassembly and no fire within seven days of the test.</p>				
样品状态 Sample status	<p>C21#~C30#: 第一个循环完全放电的电芯； C21#~C30#: first cycle in fully discharged states; C31#~C40#: 第二十五个循环完全放电的电芯。 C31#~C40#: after 25 cycles in fully discharged states.</p>				
样品编号 Sample No.	测试结果 Test result	备注 Remark	样品编号 Sample No.	测试结果 Test result	备注 Remark
C21#	O	/	C31#	O	/
C22#	O	/	C32#	O	/
C23#	O	/	C33#	O	/
C24#	O	/	C34#	O	/
C25#	O	/	C35#	O	/
C26#	O	/	C36#	O	/
C27#	O	/	C37#	O	/
C28#	O	/	C38#	O	/
C29#	O	/	C39#	O	/
C30#	O	/	C40#	O	/
<p>注：D-解体； R-破裂； F-起火； O-无解体、无破裂、无起火。 Note: D-Disassembly, R-Rupture, F-Fire, O-No Disassembly, No Rupture & No Fire.</p>					

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

地址：中国广州市天河区珠江新城花城大道66号B座

网址：www.iqtc.cn 邮编：510623

Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China

Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)



Date: 2020-08-05

Page: 13 of 14

样品图片

Photo of the sample

电池与电芯/Battery and Cell

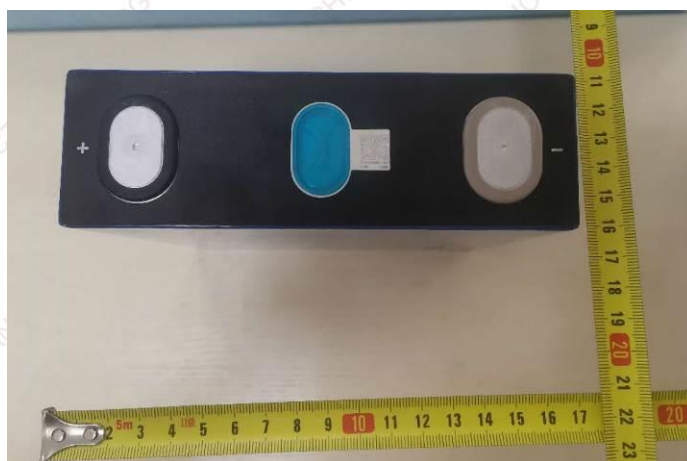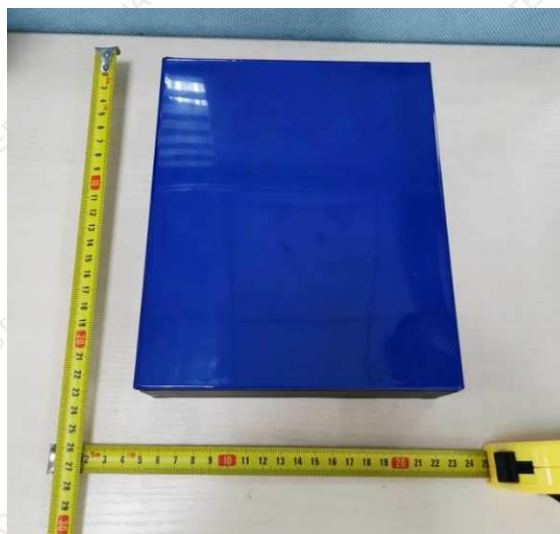

1. 本报告结果仅对测试样品负责。The results in this report are relevant only to the sample(s) tested.

2. 未经签发机构书面同意，不得部分引述或复制本报告。Without written permission of IQTC, this report shall not be quoted or reproduced except in full.

广州海关技术中心

GUANGZHOU CUSTOMS DISTRICT TECHNOLOGY CENTER



中国认可
国际互认
检测
TESTING
CNAS L2322

地址: 中国广州市天河区珠江新城花城大道66号B座
网址: www.iqtc.cn 邮编: 510623
Add: Tower B, No.66 Huacheng Avenue, Zhujiang Xincheng, Tianhe District, Guangzhou, China
Website: www.iqtc.cn Postcode: 510623

No: 01052000003024-1(E)

Date: 2020-08-05

Page: 14 of 14

声明 Statement

1. 本报告无检验单位公章无效。

The test report is invalid without the official stamp of IQTC.

2. 本报告无批准人、审核人及主检人签名无效。

The test report is invalid without the signatures of Approver, Checker and Appraiser.

3. 本报告涂改无效。未经本实验室书面同意, 不得部分地复制本报告。

The test report is invalid if altered. Nobody is allowed to photocopy or partly photocopy this report without written permission of IQTC

4. 客户必须如实提供样品及资料, 并保证申报品名和样品以及运输货物相同, 否则本检测单位不承担任何相关责任。

The client should provide samples and relevant data, at the same time, they should guarantee the consistence of the product's name they declared, the samples they provided and the goods to be transported. Otherwise we will not bear any relevant responsibilities.

5. 对检验报告若有异议, 应于收到报告之日起十五天内向检验单位提出。

Objection to the test report must be submitted to IQTC within 15 days

6. 本报告仅对送检样品负责。

The test report is valid for the tested samples only.

7. 检验地址: 广东省广州市科学城南翔支路1号C102房(轻工科学城实验室)

Inspection Address: Room C102, No.1 Nanxiangzhi Road, Science City, Guangzhou, Guangdong, China (Light Industry Testing Laboratory in Science City)

电话(Tel): 020-38669019

电子邮箱(E-mail): itl@iqtc.cn

* * * * 报告结束 End of report * * * *